

A sample from the Broburg site in Sweden. Cutaway shows molten areas of the sample; solid areas show unreacted material.

Ensuring longevity: Ancient glasses help predict durability of vitrified nuclear waste

By Jamie L. Weaver, John S. McCloy, Joseph V. Ryan, and Albert A. Kruger

Ancient glass artifacts provide a surprisingly rich source of analogues to study long-term mechanisms of glass alteration for design of new glasses for nuclear waste disposal.

How does glass alter with time? For the last hundred years this has been an important question to the fields of object conservation and archeology to ensure preservation of glass artifacts.¹ This same question is part of the development and assessment of durable glass waste forms for the immobilization of nuclear wastes. Researchers have designed experiments ranging from simple to highly sophisticated to answer this question and, as a result, have gained significant insight into the mechanisms that drive glass alteration. However, gathered data have been predominately applicable to only short-term alteration—i.e., over the course of decades.

Long-term mechanisms of glass alteration have remained elusive.² These mechanisms are of particular interest to the international nuclear waste glass community, because it strives to ensure that vitrified products will be durable for thousands

to tens of thousands of years. For the past three decades, this community has been attempting to fill this research gap by partnering with archeologists, museum curators, and geologists to identify hundred-to million-year-old glass analogues that have altered in environments (Figure 1) representative of those expected at potential nuclear waste disposal sites. Even with these partnerships, the process of identifying a waste glass relevant analogue is challenging; it requires scientists to relate data collected from short-term laboratory experiments to observations made from long-term analogues and extensive geochemical modeling.

Choosing an appropriate analogue: Initial considerations

When initially approaching the challenge of determining a glass alteration analogue, one could choose to limit the types of glasses to those that have compositions similar to nuclear waste glasses. Although it is very unlikely that an analogue will have exactly the same composition as a nuclear waste glass, it is important to study glasses that contain similar mass percentages of the baseline oxides of silica, aluminum, sodium, and, if possible, boron.

The difficulty of finding a one-to-one analogue is in part due to the complex elemental composition of nuclear waste. In general, the two most common types of vitrified

nuclear wastes are low activity waste (LAW) and high-level waste (HLW). Classification of these wastes is most often based on present radionuclides and regulations regarding how these radioactive elements are immobilized and isolated from the environment. Additionally, researchers further distinguish glasses by their relative elemental concentrations.

For U.S.-based LAW glasses, baseline components are typically ~45 mass% SiO₂ and ~20 mass% Na₂O, mixed with ~6 mass% Al₂O₃, ~9 mass% B₂O₃, and ~20 mass% of other waste-derived oxides. Alternatively, U.S.-based HLW glasses contain ~30–55 mass% SiO₂, ~15–20 mass% Na₂O, ~4–22 mass% Al₂O₃, and ~5–20 mass% B₂O₃, with other oxides comprising the balance, either added in the frit or from the waste stream. HLW glasses also may contain more iron than LAW glasses. Depending on the origin of the waste stream—i.e., industrial waste from used nuclear fuel reprocessing or legacy defense nuclear waste—these other elements can vary widely in identity, concentration, and oxidation state.

Once a waste glass of interest is identified and its compositional range defined, then it is possible to begin looking for an appropriate analogue or set of analogues (Figure 1). An ideal analogue, as stated above, should contain most, if not all, of the main elements in the waste glass in

Credit: Tamas Varga, Carolyn Pearce, and Mike Perkins (PNNL).

Capsule summary

THE CHALLENGE

Studying how glass alters over time, especially large spans of time, is a challenging research problem. However, thorough understanding of these mechanisms is critical for prediction and design of glasses that can safely store nuclear waste for long periods of time.

WHAT'S OLD IS NEW AGAIN

Ancient artifacts represent a rich source of material to study long-term glass alterations under various environmental and exposure conditions. Although artifacts often have compositions different from new glasses, they offer many potential analogues for study.

FUTURE MODELS

Better understanding of long-term glass alteration allows more accurate prediction of the performance of vitrified nuclear waste to help develop waste glasses that will be durable for many millennia.



mass% that fall within the composition range defined for the waste glass. Many previously studied analogues (see below) have two or three of the main elements of their corresponding waste glasses. In these cases, a second set of analogues that contains the relevant mass% of the other primary elements—and do not deviate more than a few mass% of the other elements—could be identified and studied. Combining both data sets could allow a researcher to develop a well rounded view of how major elements affect the long-term durability of waste glass.

Additionally, studying two or more analogues may provide insight into how a slight change in composition affects the overall durability of a sample. Understanding these interactions is important because glasses produced during vitrification often vary slightly from one melt batch to the next. These differences in composition are intentional and are designed to accommodate the special chemistry of a particular waste stream and to efficiently incorporate the waste elements into the glass.

Parallel to selecting an analogue that has a similar composition as the waste glass of interest, it also is important to choose an analogue that has been altered under relevant conditions. This is because how a glass alters can be partially determined by its altering environment.³ A candidate glass analogue should come from alteration environments similar to those that have been suggested or chosen for the disposal of nuclear waste glasses. Disposal areas are often designed to have engineered barriers, such as clay and granite, which will

Figure 1. Locations and timeline of various types of excavated vitreous materials used as analogues to study durability of modern nuclear waste glasses.


dictate chemistry of the environment in contact with the glass.

Analogues are samples with a past

In addition to the above considerations, scientists also collect information regarding the provenance, or history, of a possible glass analogue. They often mine this data from archeology, art conservation, and geology journals, or gather data through interviews with museum staff, geologists, or archaeologists who have studied the glass. Scientists can then use these findings to answer three subsequent questions about the analogue:⁴

- Is it ethical or feasible to analyze this glass?
- What ex-situ factors may have affected how this glass was altered, and what effects did they have?
- How does studying this glass help validate current glass alteration models?

Researchers should be aware of any cultural importance of a possible glass analogue and should carefully consider what physical and philosophical effects any analysis might have on an artifact's long-term preservation. Researchers should ask whether analyzing the glass will change how it may be interpreted by

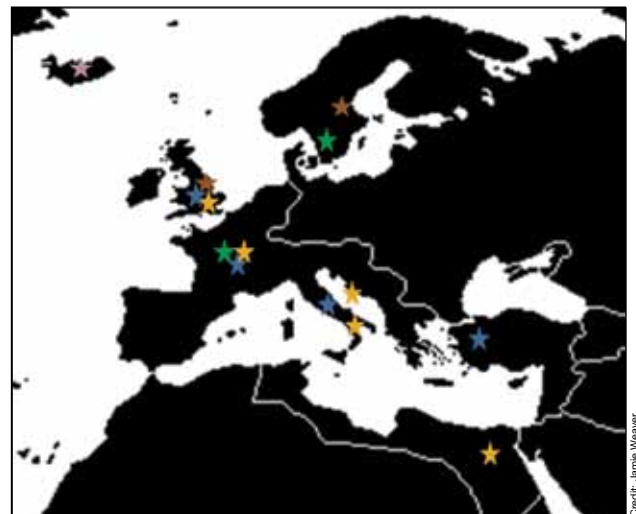

future generations. It is important that researchers make these considerations with the advice of conservators, archeologists, art historians, and museum curators who specialize in the time period and geographical area associated with the artifact.

In all cases, an approved analogue should be analyzed using nondestructive methods if possible. However, if some destructive analysis is warranted to obtain critical information that otherwise could not be obtained, researchers must consider additional precautions. For instance, they should consider how destructive methods will alter the glass. They should be aware of what information they are removing from the object during analysis. They also need to consider what chemical changes the analysis technique might induce in the object, and whether this will impact its future preservation or interpretation.

Scientists studying the analogue also should consider how collected data can help validate or invalidate current glass alteration models. As stated in question

Ensuring longevity: Ancient glasses help predict durability of vitrified nuclear waste

three, a scientist should be aware of what part of the alteration model is being tested, which requires knowledge of glass corrosion science and theory.

Scientists should also consider what effect outside factors may have had on the alteration of glass analogues. Glass alteration models are developed from data collected on controlled experiments, but analogues are rarely altered under controlled conditions. Variability in alteration conditions could include annual changes of the pH of the groundwater that was in contact with the analogue, or fluctuations in microbial populations in

the soil surrounding a buried analogue. It can be difficult to know all factors that might have influenced alteration of an ancient glass during its history, and it can be challenging to separate out the effects of each factor. However, simplified experiments performed in a laboratory setting can help disentangle these factors.

Data collected in the analysis of ancient glasses also can be utilized in preservation and historical interpretation of the artifact itself or similar pieces. For example, archeologists continue to attempt to gain an understanding of the methods used to make glass recovered at the Broborg site in

Sweden (Figure 2 and sidebar). Scientists hope that further analysis of ancient glasses may uncover redox conditions used by these ancient peoples and demonstrate a connection between iron working from that time and creation of the glasses.

Previous studies

Natural glasses

Most early studies of ancient glasses for the purpose of model validation have focused on alteration of natural glasses, such as basalts, tektites, and rhyolites.⁸⁻¹⁰ Rhyolitic glasses are high-silica natural volcanic glasses also known as obsid-

Broborg hillfort case study

Archeologists define vitrified forts as stony fortifications in which a dry-wall structure has been bound by molten or calcined materials.⁵ Over the past 60 years, scientists have produced three theories of how hillforts were vitrified: *incidental*, or resulting from cooking-hearth fires, forges, or even lightning; *constructive*, meaning materials were purposefully selected and melted to fortify dry-wall structures; and *destructive*, meaning walls surrounded by organic matter, such as timber, that was set on fire either by accident or during an attack.⁶

In the case of the Broborg hillfort, located near Uppsala, Sweden, scientists believe that vitrification was intentional, and its construction was completed around 500 CE during the Migration Period (prior to the Viking age). Several excavations of the site have resulted in evidence of house foundations, suggesting that at one point it held a permanent settlement. Walking along the edge of the partially vitrified wall at the site, a casual observer will find it initially difficult to discern rock from vitrified material. However, Peter Kresten—a geologist who has spent most of his professional career investigating vitrified forts—can provide guidance that makes differences between the two materials apparent. Atop and between about one-third of the well-weathered black-and-white-speckled granite and gneiss boulders lie smooth sections of amphibolite melt. With further survey of the site, one can see that the areas where the boulders were not covered and fused with vitrified matter are more heavily eroded than their fortified counterparts. When the dust is lightly swept away from vitrified sections, one discovers a slightly cloudy material that ranges in colors from dark brown to almost clear and, in some areas, still bears marks of the charcoal used in its firing.

Amphibolite appears to have played an important role in the construction of Broborg and has



(left) Jamie Weaver at the Broborg hillfort near Uppsala, Sweden, where remains of a vitrified wall are protruding from the snow. (right) Close-up of a molten section from a hillfort, showing impressions of the charcoal used to vitrify the materials, despite ~1,000 years of weathering.

led researchers at Washington State University and Pacific Northwest National Laboratory to dig into the geology of this region of Sweden. The amphibolite used at the site is metamorphic doleritic rock formed at high water pressure and contains mainly hornblende and feldspars. Studies of the amphibolite left at the site have uncovered evidence of a wide range of localized melting and moisture evolution, from slight heating to complete liquefaction. WSU scientists have found that temperatures >1,400°C are needed to create a molten material if the melting is completed in air without

the aid of bellows. Other studies have found that amphibolite collected from the site could be melted only with the help of a forced draft and a furnace hearth covered with turf.⁷ These results suggest that to create vitrified portions of the wall, ancient people most likely had to control redox condition and water content of the melt—a technology they most likely developed based on their experiences with iron smelting. Understanding how these melts were made could inform their chemistry, which is invaluable in determination of the long-term durability of Broborg glasses. ■



(left) Melt series based on chemistry of melted amphibolite composition from the Broborg site. Melting in atmosphere and without the use of bellows required heating the material to temperatures >1,400°C, which is not likely to be reached in ancient times. (right) Final glass produced from the melting study.



Credit: John McCoy



Credit: John McCoy

Figure 2. Examples of hillfort glasses, which are manufactured glasses with compositions similar to some nuclear waste glasses. An amphibolite rock source for vitreous material, found at Broborg in Sweden, shows a molten top portion.

ian. These natural glasses range from hundreds of millions of years old (such as terrestrial, meteoritic, and lunar glasses) to only thousands of years old (some basaltic and rhyolitic glasses).

Tektites and rhyolitic glasses generally have high SiO₂ concentrations (70–75 mass%), whereas basaltic glasses have lower SiO₂ content (45–50 mass%). Unlike most nuclear waste glasses, natural glasses tend to contain low mass percentages of alkali elements. This low alkali content has made application of the alteration data collected on these natural glasses to most alkali-rich waste glasses difficult. However, even with these limitations, basaltic glasses have been used as fruitful analogues to some HLW glass formulations.¹¹

Roman glasses

An excellent example of using anthropogenic glass analogues for modeling glass alterations can be found in the recent works of Verney-Carron and the Commissariat à l'Énergie Atomique (CEA) on fractured, ~1,800-year-old glass blocks excavated in 2003 from a Roman shipwreck near the French island of Embiez.¹² Many glasses—including nuclear waste glasses—fracture on cooling, and these fractures increase the reactive surface area of the glass. Because of the slow flow of water in and out of some cracks, increased surface area results in alteration rates in the cracks different from those on the exterior glass

surfaces. The effects of these cracks on long-term alteration rates have been difficult to replicate in short-term laboratory tests because of the slow rate at which borosilicate glass alters.

In addition to showing that alteration mechanisms of archeological glass are similar to those described by a modern glass alteration model, the authors also discovered that alteration kinetics slightly varied depending on fracture location. They calculated a lower alteration rate for internal cracks that were not continually exposed to water as compared with exterior surfaces that were most likely in constant contact with water. Without renewal of fluid into cracks, the altering solution became saturated with dissolved glass elements, making it unfavorable for the glass matrix to undergo further dissolution.

In a recent follow-up to this study, Verney-Carron et al.¹³ used chemical modeling to simulate alteration of the glass in a variety of solutions, and they compared the results with reactive transport modeling of alterations in the cracks. They calculated that cracks inside the archaeological blocks had one to two orders of magnitude less alteration than the external surface because of strong coupling between rate of glass alteration and slow renewal of the internal crack altering solution. Additionally, narrow internal cracks precipitated crystals because of supersaturation of the solution in the crack with silicon, calcium, and aluminum. Formation of these crystals plugged the cracks, causing flow of water and alteration processes to halt.

On this side of the Atlantic, glass scientists at PNNL have been working with Italian archeologists to investigate the formation of alteration layers on second- to third-century CE Roman glass recovered from the *Iulia Felix* shipwreck.¹⁴ The *Iulia Felix* wreck is of particular interest, because its cargo included blue-green Roman glass fragments (Figure 3)—referred to in archeology literature as “naturally colored” glasses—and colorless and red shards, “artificially colored” by additions of reduced copper. Because ancient glassmakers usually added coloring agents in measured amounts to colorless glasses, artificially colored glass usually has a base composition similar to naturally colored Roman glasses. This slight modification makes it possible to investigate the effect of chemical composition on glass alteration within a set



Credit: Denis Strachan, Joe Ryan

Figure 3. Fragment of a Roman glass cup handle found in the *Iulia Felix* shipwreck, showing iridescent alteration layers.

environment. Further research is currently underway on these artifacts.

PNNL researchers have also focused on parts of these glasses that were encased in cemented sediments.¹⁴ The cementing material around the glass is magnesium-rich calcite, likely formed through corrosion of the glass in seawater saturated with naturally occurring dolomite and magnesium silicate precipitations. These magnesium silicate species form during alteration of some HLW glasses, and researchers identified similar species in the altering solution of nuclear waste glasses that were subjected to corrosion with a 1 mmol/kg MgCl₂ solution.^{15,16} Both cited experiments were short term, but, when coupled with results from the *Iulia Felix* glasses, the researchers determined that, in undersaturated conditions, dissolution of the glass matrix is the main cause of formation of cementing phases. Burial materials in contact with glass are important in determining alteration conditions, and, if possible, fragments should be collected with sediments in place (Figure 4).

Iron slag

Many scientists have gained insight from other ancient vitreous materials in addition to glasses. A few studies in recent years have focused on alteration of metallurgical slags—glassy materials produced when metals are smelted from ore.¹⁷ Slag is comprised of a mixture of metal oxides, typically calcium oxide, and silica. Iron blast furnace slags, for instance, are formed from silica in the iron ore and added limestone or a similar calcium source. Similar vitreous materials may form when clays from furnaces are heated to high temperatures when processing iron (Figure 5). Aged slags produced during ironworking represent an

Ensuring longevity: Ancient glasses help predict durability of vitrified nuclear waste



Credit: Denis Strachan

Figure 4. Glass collected in-situ with contacted soil at the Aquileia site in Italy. Aquileia was a major glass-producing center in Roman times.

alteration condition in which silica-rich materials are altered in the presence of metallic iron. This situation is similar to what may happen to nuclear waste glass as it ages in stainless-steel containers.

Researchers identified such altered slags from the 16th century CE and recovered from an excavated blast furnace site located in Normandy, France. Geological conditions of the burial (saturated clay) are similar to those described for disposal of some waste glasses in France. French scientists at the CEA have studied these samples using short-term wet laboratory experiments as well as analysis of long-term alteration layers on the artifact surfaces.¹⁷

Researchers designed wet laboratory experiments to closely reproduce the proposed French nuclear waste disposal settings. They covered SON68, a non-radioactive version of a French HLW glass, with an iron-steel composite and injected it with a synthetic solution at a flow rate chosen to test the glass under diffusion-controlled conditions. The researchers also used this alteration routine on synthetic archeological slags that had the same composition as excavated samples. They determined significant similarities in the increase of glass alteration in the presence of iron from comparison of the two altered samples. This result supports previous studies that have shown a deleterious effect of reduced iron, which results in an increased rate of glass dissolution, an important result that researchers can use to aid modeling of long-term durability of glasses stored in iron-based containers.¹⁸

Swedish hillfort glasses

Researchers recently have identified glasses that were produced almost 1,500

years ago on a hillfort in Sweden that have been altered by surface atmospheric conditions, which have analogies to the near-surface disposal planned for some low-level nuclear waste glasses, including those at Hanford.¹⁹ A hillfort is a building structure used as a fortified refuge, trading post, or defended settlement, where an elevated location relative to the surrounding area provides a defensive advantage.²⁰ There are many hillforts in Europe, and these fortifications usually follow the contours of a hill, consist of one or more lines of earthworks (including stockades or defensive walls), and are surrounded by external ditches. More than 100 of the European hillforts, most from the Iron Age, are vitrified, and much controversy continues to surround how this occurred (see sidebar).²⁰

A selection of glasses from the Broborg hillfort site in Sweden contain iron at concentrations between those detected in basaltic and Roman glasses. Similar to basaltic glasses, some of the Broborg glass samples contain embedded crystalline phases, such as magnetite and other spinels. The current acceptance criteria for Hanford LAW glasses allow up to a few vol% of spinel crystals. The hillfort vitrified material remains exposed today to surface weathering cycles or, in some cases, is shallowly buried by local soil.⁷ Although research on these ancient vitreous materials remains in its early stages, WSU researchers have made promising headway in an attempt to synthetically reproduce these glasses. In addition, PNNL researchers have been working with Swedish archeologists, scientists, and state officials to acquire fresh near-surface altered samples from the Broborg site.

Medieval glasses

It is sometimes helpful to analyze a glass that has been altered under two or more conditions simultaneously. In these cases, the focus of understanding is placed on whether a glass alteration model can be extrapolated to include multiple altering conditions. Alteration data from several environments can be extremely helpful when attempting to



Credit: Jamie Weaver

Figure 5. Scientific collaboration at work in Uppsala, Sweden, showing investigation of vitrified iron furnace walls. Shown (left to right) are John McCloy, glass scientist of Washington State University; Eva Hjärthner-Holder, archaeometallurgist in Arkeologerna, Geoarkeologiskt Laboratorium; and Rolf Sjöblom, geochemist with Tekedo and Luleå University of Technology.

decide what disposal setting and geology is best for a specific type of waste glass. Researchers have discovered medieval stained and nonstained glass windows to be ideal analogues for these studies, because the windows often have undergone alteration under two or more settings²¹—glass window panels facing outward are exposed to an alteration environment different from those facing inward. A few rare glass samples that have been found in architectural structures have also been excavated from groundwater-saturated soils,²¹ thus providing a third environment to compare alteration data.

Because builders, craftsmen, and church officials kept excellent records, medieval glass-manufacturing methods of most stained glass windows are well-known. Therefore, glass scientists can identify conditions under which the glasses were made. In most cases, craftsmen made medieval glasses in either soda (sodium-rich) or potash (potassium-rich) compositions through melts of a blend of washed siliceous sand and a flux.²² The flux material was either plant-based (beech or fern ash) or mineral-based (natron) and, when added to other glass-forming materials, lowered the melting temperature.

Glassmakers achieved color either by adding metals or oxides of cobalt, chromium, manganese, copper, or iron and controlling redox conditions of the melt, or by applying a thin layer of a previously colored glass to the surface of a clear glass. Minor components in these medieval

glasses are thus transition metals that are relevant to some nuclear waste glasses. Chemical durability different from the sodium-rich versus potassium-rich glasses as well as presence of multiple compositions with various transition metals provide a large dataset for studying composition-dependent alterations as well.

Scanning electron microscopy studies on medieval stained glasses from England, Italy, and France have revealed that the type of weathering has an effect on thickness and structure of the alteration layer(s). Potash glasses exposed to an exterior environment produce thick, uneven alteration layers with some pitting, along with pervasive micro-cracking.²³ In contrast, potash glasses that have been buried and exposed to groundwater have nearly even alteration layers with little to no cracking.

Potential future glasses for study

There are many less-well-studied ancient glasses from around the world that deviate significantly in composition from the glasses described above. These glasses could provide researchers with new insights into the effects of compositional and environmental differences on glass alteration. These include high-alumina glasses from India and some regions in Turkey, a special subset of Byzantine glasses that contain a moderate level of alumina plus some boron,²⁴ and certain Chinese glasses with high barium oxide content. Researchers currently are considering some of these glasses as possible analogues, although their rarity makes them challenging to acquire for study.

Researchers also need to identify high-concentration boron (~10 mass% B₂O₃) aluminosilicate glasses that have been altered in waste-disposal-relevant environments. Boron is a primary component in all waste glasses and has increased, in certain cases, the durability of silicate glasses.²⁵

Boron made its mark on the glass industry in the early 1900s, when Corning patented a series of boron-containing silicate glasses that could withstand temperature shock—Pyrex.²⁶ At this time, there were many recorded accidents related to breakage of hot glass railway lanterns during cold rainstorms. Glass breakage caused the railway signals to fail, catching innocent people unaware of oncoming trains. Replacing soda in the

glass with boron oxide solved the glasses' thermal shock problem.

Today, we find borosilicate glasses in almost every home, office space, and laboratory. In addition, commercial uses have utilized the poor durability of some boron-containing glasses. One example is Vycor, in which a phase-separated sodium borosilicate glass is selectively leached of its sodium borate phase, leaving a skeletal silicate network that is usually further consolidated to produce a low-cost nearly pure silica. Clearly, chemical durability concerns are relevant to ancient materials and to today's and likely tomorrow's commercial glass processing.

Challenges remain

The studies reviewed above are only a portion of those conducted to date on ancient glasses.^{27,28} However, their relevance to the validation of glass alteration models is significant. There are many challenges associated with analyzing ancient glasses for this purpose. However, the payoff of having a composition- and environment-dependent model of glass alteration validated by many data points, spanning days to millions of years, will be momentous. A better understanding of long-term glass alteration will allow for a more accurate prediction of the long-term performance of vitrified nuclear waste and could aid continued formulation of waste glasses that will be durable for "thousands of years".² In the process, knowledge gained on glass alteration can help create industrial glasses with engineered durability as well as help museums and historical societies in the preservation of cultural heritage objects.

About the authors

Jamie Weaver is a Ph.D. student in the Department of Chemistry at Washington State University (Pullman, Wash.) and a Ph.D. intern at PNNL. Joseph Ryan is with the Energy and Environment Directorate at Pacific Northwest National Laboratory (Richland, Wash.). John McCloy is associate professor in the School of Mechanical and Materials Engineering at Washington State University and a joint appointee with Pacific Northwest National Laboratory. Albert Kruger is with the Office of River Protection at the Department of Energy (Richland, Wash.).

References

1. R.H. Brill, "The record of time in weathered glass," *Archaeology*, **14** [1] 18–22 (1961).
2. C.M. Jantzen, K.G. Brown, and J.B. Pickett, "Durable glass for thousands of years," *Int. J. Appl. Glass Sci.*, **1** [1] 38–62 (2010).
3. B. Dal Bianco, R. Bertonecello, L. Milanese, and S. Barison, "Glasses on the seabed: Surface study of chemical corrosion in sunken Roman glasses," *J. Non-Cryst. Solids*, **343** [1–3] 91–100 (2004).
4. W.M. Miller, N. Chapman, I. McKinley, R. Alexander, and J.A.T. Smellie, Eds., *Natural analogue studies in the geological disposal of radioactive wastes*. Elsevier, New York, 2011.
5. E. Youngblood, "Celtic vitrified forts: Implications of a chemical-petrological study of glasses and source rocks," *J. Archaeol. Sci.*, **5** [2] 99–121 (1978).
6. P. Kresten and B. Ambrosiani, "Swedish vitrified forts—A reconnaissance study," *Formånnen*, **87**, 1–17 (1992).
7. P. Kresten, L. Kero, and J. Chyssi, "Geology of the vitrified hill fort Broborg in Uppland, Sweden," *GFF*, **115** [1] 13–24 (1993).
8. J. Crovisier, H. Atassia, V. Dauxa, J. Honnorez, J. C. Petita, and J. P. Eberhart, "A new insight into the nature of the leached layers formed on basaltic glasses in relation to the choice of constraints for long term modelling," *MRS Proceedings* **127**. Cambridge University Press, Cambridge, U.K., (1988).
9. I. Techer, T. Advocat, J. Lancelot, and J.-M. Liotard, "Basaltic glass: Alteration mechanisms and analogy with nuclear waste glasses," *J. Nucl. Mater.*, **282** [1] 40–46 (2000).
10. M.C. Magonhier, J.C. Petit, and J.C. Dran, "Rhyolitic glasses as natural analogues of nuclear waste glasses: Behaviour of an Icelandic glass upon natural aqueous corrosion," *Appl. Geochem.*, **7** [Supplement 1] 83–93 (1992).
11. B. Parruzot, P. Jollivet, D. Rebiscoul, and S. Gin, "Long-term alteration of basaltic glass: Mechanisms and rates," *Geochim. Cosmochim. Acta*, **154**, 28–48 (2015).
12. A. Verney-Carron, S. Gin, and G. Libourel, "A fractured Roman glass block altered for 1800 years in seawater: Analogy with nuclear waste glass in a deep geological repository," *Geochim. Cosmochim. Acta*, **72** [22] 5372–85 (2008).
13. A. Verney-Carron, S. Gin, P. Frugier, and G. Libourel, "Long-term modeling of alteration-transport coupling: Application to a fractured Roman glass," *Geochim. Cosmochim. Acta*, **74** [8] 2291–315 (2010).
14. D.M. Strachan, J.V. Crum, J.V. Ryan, and A. Silvestri, "Characterization and modeling of the cemented sediment surrounding the Iulia Felix glass," *Appl. Geochem.*, **41**, 107–14 (2014).
15. B. Grambow and D. Strachan, "Leach testing of waste glasses under near-saturation conditions," pp. 623–34 in *Scientific basis for nuclear waste management VII*. North-Holland, New-York, 1984.
16. T. Maeda, H. Ohmori, S. Mitsui, and T. Banba, "Corrosion behavior of simulated HLW glass in the presence of magnesium ion," *Int. J. Corros.*, **2011**, 796457 (2011).
17. A. Michelin, E. Leroy, D. Neff, J.J. Dynes, P. Dillmann, and S. Gin, "Archaeological slag from Glinet: An example of silicate glass altered in an anoxic iron-rich environment," *Chem. Geol.*, **413**, 28–43 (2015).
18. E. Burger, D. Rebiscoul, F. Bruguier, M. Jublot, J.E. Lartigue, and S. Gin, "Impact of iron on nuclear glass alteration in geological repository conditions: A multiscale approach," *Appl. Geochem.*, **31**, 159–70 (2013).
19. R. Sjöblom, H. Ecke, and E. Brännvall, "Vitrified forts as anthropogenic analogues for assessment of long-term stability of vitrified waste in natural environments," *Int. J. Sustain. Dev. Plann.*, **2013**.
20. D. Harding, *Iron age hillforts in Britain and beyond*. Oxford University Press, Oxford, U.K., (2012).
21. J. Sterpenich and G. Libourel, "Using stained glass windows to understand the durability of toxic waste matrices," *Chem. Geol.*, **174** [1] 181–93 (2001).
22. J. Henderson, "The raw materials of early glass production," *Oxford J. Archaeol.*, **4** [3] 267–91 (1985).
23. T. Lombardo, L. Gentaz, A. Verney-Carron, A. Chabas, C. Loisel, D. Neff, and E. Leroy, "Characterisation of complex alteration layers in medieval glasses," *Corros. Sci.*, **72**, 10–19 (2013).
24. T. Rehren, P. Connolly, N. Schibille, and H. Schwarzer, "Changes in glass consumption in Pergamon (Turkey) from Hellenistic to late Byzantine and Islamic times," *J. Archaeol. Sci.*, **55**, 266–79 (2015).
25. R.W. Revie and H.H. Uhlig, *Uhlig's corrosion handbook*, Vol. 51. Wiley, New York, 2011.
26. W.B. Jensen, "The origin of pyrex," *J. Chem. Educ.*, **83** [5] 692 (2006).
27. R.H. Brill, *Chemical analyses of early glasses*, Vol. 2: Tables. The Corning Museum of Glass, Corning, New York, N.Y. (1999).
28. J. Henderson, *Ancient glass: An interdisciplinary exploration*. Cambridge University Press, Cambridge, U.K. (2013). ■



Challenges in assessing the mechanical behavior of coatings on architectural glass

Glass coatings can reduce building energy demand, but thorough understanding of the mechanical properties of these multilayer coatings is needed.

By Steve J. Bull

One of the most significant uses of glass is in architecture—building applications accounted for ~70% of worldwide glass sales in 2012. If we consider that ~40% of the world's energy demand is used to heat, cool, and light buildings, then glass coatings become a significant source of potential energy savings. Suitable glazings can reduce energy demand, helping keep buildings warm in cold climates and cool in hot climates, while allowing transmission of light. For this reason, demand for energy-efficient glazings is increasing.

Glass is mostly opaque to ultraviolet light, but transparent to visible and infrared light. For energy efficiency, glass needs to decrease infrared transmission without compromising visible light transmission. Low emissivity or energy-efficient glazings usually are based on a thin, transparent conducting layer, which may be a single layer or part of a multilayer stack with surrounding antireflection and barrier coatings. The main design factor is optical performance of the coating, but mechanical damage, particularly caused by transport or storage, also is a consideration. In most cases, a supplier produces the coatings, and the supplier delivers the coated product to a fabricator who cuts and assembles the glass into windows. Coated glass may be rejected if it is damaged in transit and if the damage affects optical performance. Therefore, an understanding of the mechanical response of multilayer coatings on glass is essential to reduce losses from damage.